

Withdrawal Strength of Nail-Timber Joints for Kenyan Grown Cypress and Pines

George Muthike

Kenya Forestry Research Institute
Forest Products Research Centre
P. O. Box 64636 -00620. Nairobi, Kenya.

Fred Muisu

Department of Forestry and Wood Science
Chepkoilel University College

Joseph Githiomi

Kenya Forestry Research Institute
Forest Products Research Centre
P. O. Box 64636 -00620. Nairobi, Kenya.

Abstract

Nailed joint specimens of general structural and special structural grade cypress and pine timber were constructed and tested to determine the withdrawal resistance. The main objective of this study was to generate a database for basic withdrawal loads for nailed Kenyan grown cypress and pine timber joints for use in the development of timber structural design codes. Timber specimens were sampled from the sawmills in all plantation growing areas. Seventy two pairs of matched 50mm by 25mm by 300mm joint members were prepared from the timber then conditioned to an equilibrium moisture content of about 16 to 18 percent. The members were laid on a hard flat surface and nails driven into them using a claw hammer in a direction perpendicular to grain. Each specimen was subjected to a withdrawal load in a USTM and strength determined according to British Standards (BS 6948: 1989). The maximum load and mode of failure were recorded. Statistical analysis was done using General Linear Model and ANOVA tools in Statistical Package for Social Sciences. Results showed that wood species, grade, nail size and penetration had a significant effect on the nail withdrawal strength. The differences between species and grade are due to variation in specific gravity of the wood species and increased fastener contact area with increased penetration. Special structural graded wood (SS) and six inch nails yielded significantly higher strength for both pine and cypress than general structural (GS) and other nail lengths. Nailed pine and cypress joint strengths are comparable to those of species with similar specific gravity. These findings imply that establishment of withdrawal strength design values should put into account the combined effect of these factors.

Keywords: withdrawal strength, Nails, timber grade, nailed timber joints.

Introduction

The strength and stability of any structure depends to a large extent on the joints that hold its parts together. The design and construction of timber joints is very critical because they form the weakest links in most engineered wooden structures (Soltis *et al*, 1994; Mohammad, 1996). Wood can easily be joined together with a wide variety of fasteners including nails, screws, bolts, staples and metal connectors of different types and shapes (USDA Forest Service, 1987).

Nails are the most commonly used fasteners for structural construction such as trusses, as they are light and easily applied using hammers or nailing guns. Nailed joints are considered effective when nails are driven into the wood without visible splitting of the wood. In addition, strong joints are achieved if wood is nailed at moisture content at or close to the equilibrium moisture content of the exposure conditions (Mohamad and Smith, 1996).

Smooth round wire nails for example tend to lose some grip on the wood when moisture is lost from the wood due to wood shrinkage around the nail. In timber construction, nails can resist forces tending to cause direct separation of the joined members (Mohamad and Smith, 1994). Such forces include withdrawal and lateral loads or a combination of both. The strength of the joint depends on the resistance to the joint failure. Nail resistance to withdrawal depends on wood density, nail diameter, depth of penetration, surface conditions of the nail at the time of driving in and use conditions (USDA Forest Service, 1987; Soltis *et al*, 1994). Higher withdrawal resistance could result from high wood density, large nail diameter, deeper penetration and clean, rust free nail surface (USDA Forest Service, 1987) as well as increased spacing for nail rows (Blass, 1994). However, high density wood split easily hence limiting the end distances of members and nail diameters applicable to timber joints.

Less dense wood on the other hand split less and can thus allow the use of more nails or nails of large diameters. This knowledge has for a long been applied in design and construction of structures in Kenya using British and other Standards. However, the use of such design codes locally may lead to design deficiencies because the design information is specific to temperate wood species whose characteristics differ appreciably from locally grown species. Variations in wood density of locally grown pines and cypress have been recorded between species (Ringo, 1983) and within species (Chikamai, 1987).

Similarly, within tree variation in wood density has been observed in juvenile and mature wood (Muthike, 2003). Timber grading has been shown influence its utilization potential irrespective of the species and application (Chikamai, *et al*, 2001). A good design code must therefore put into account the variability in wood physical and mechanical properties as well as the differences in joint capacities due to such variability.

The efficient utilization of timber for structural purposes requires adequate knowledge of strength properties of mechanically fastened joints. Test standards used in different countries give the basic requirements for nailed joints based on wood materials in those countries. As a result of differences in wood characteristics, especially density, such standards are only reliable when designing wood whose characteristics are considered in the development of the standard. The current design codes in Kenya do not address this adequately hence the need for local standards that are directly applicable to design with Kenyan grown wood.

There is no data available on basic joint capacity for Kenyan species fastened with standard mechanical fasteners which necessitates evaluation of basic joint strength for various species and fasteners. This study focussed on determination of the basic withdrawal strength for various two-member mechanically fastened joints made from Kenyan grown cypress and pine timber falling under one of the two recognized grades. These two species are commonly used in the Kenyan construction industry where structural engineers need to know the fasteners basic design loads for design purposes. Nail withdrawal strength was determined for joints from two species, various sizes of nails and timber grades.

The main objective of this study was to generate basic withdrawal loads for nailed Kenyan grown cypress and pines timber joints for use in development of timber design codes. The study analyzed the effect of nail diameter, nail penetration timber species and timber grade to withdrawal strength. The data obtained from this study will be used in developing structural design codes for smooth round wire nails used in design with Kenyan grown cypress and pines.

Materials and Methods

The samples for the tests were obtained from material sampled earlier on structural size testing. The sampling had been done from all the sawmills located in all plantation growing regions covering Rift Valley, Western Rift and Eastern Rift which provided nationally growing representative sample population in all Kenyan regions. The samples sampled from each sawmill comprised of both cypress and pines. The sampled wood were graded using Kenya Bureau of Standards specification for softwood timber grades (KS02-771: 1991). For this particular testing on nail withdraw strengths, seventy two pairs of defect-free timber specimens, half of them flat sawn and the other half quarter sawn were extracted for each of the species. Timber specimens for the three nail sizes were end-matched or side-matched where end matching was not possible. The specimens were stored in controlled air conditions of $20 \pm 2^\circ$ C temperature and 65 ± 5 % relative humidity to provide an equilibrium moisture content of 16 to 18 percent or air dry material as much as possible.

Twenty four joint specimens for each nail size were prepared from the pairs of timber specimens. The nails were driven into the member using a hammer such that the shank of the nail was as perpendicular to the long axis as possible. The maximum nail penetration achieved was seven times the nominal diameter of the fastener with a minimum penetration of 30mm or a depth equal to nail length leaving a sufficient allowance for grip in the case of nails having a length less than seven times its diameter.

Test fixtures for nail withdrawal were designed and fabricated using mild steel following the specifications of British Standards (BS 6948, 1989). Preliminary tests were conducted to establish the accuracy of the test fixtures. Round nails of six inch (5.73mm diameter), four inch (3.91mm diameter) and three inch (3.40mm diameter) long, were selected from different hardware stores to ensure that they are representative of the stock in the market. The joint specimens were tested at $20 \pm 2^\circ$ C temperature and 65 ± 5 % relative humidity. A withdrawal load was applied at the underside of the head of the fastener at a continuous rate of movement of machine crosshead of 2.5 ± 0.625 mm/min for a withdrawal of at least 10 mm. The mode of failure for each specimen was noted. The maximum load for each specimen was recorded.

In order to determine moisture content and relative density, a small full cross-section sample of each member of a specimen was taken close to the fastener and weighed to an accuracy of 0.05g. The samples were dried in an oven at a temperature $103 \pm 2^\circ$ C to a constant mass and the moisture content expressed as the percentage change in mass. The relative density was expressed as the ratio of the oven dry mass to the specimen volume. Statistical analysis was done using General Linear Models (GLM) tools in Statistical Package for Social Sciences (SPSS) programme at a level of significance of 5 percent.

Results and Discussion

Analysis of variance results for the various parameters are shown in Table 1. The results show that wood species, nail penetration and wood grade have a significant effect on the nail withdrawal strength. Similar findings had been reported in USDA, Forest Product Laboratory where the withdrawal strength of a smooth nail driven into wood were found to depend on the fastener diameter, the depth of penetration of the fastener, and the wood specific gravity (Zelinka *et al.* 2012)

Although clear wood was chosen for the tests in both grades, the differences in nail withdraw strengths may have been attributed to other wood characteristics like grain orientation. Difference in wood density in cypress and pines could also have contributed to withdraw strengths in both wood species. Nail size and penetration had significant effect on withdrawal strength with penetration influencing strength more than nail diameter. This is due to the effect of the nail diameter differences and the depth differences achieved in each level of penetration (USDA Forest Service, 1987).

Table 1. Analysis of Variance for the effect of wood and nail parameters on strength

<i>Source of Variation</i>	<i>Degrees of Freedom</i>	<i>Sum of Squares</i>	<i>Mean Square</i>	<i>F value</i>	<i>Sig.</i>
Wood Grade	48	984.33	20.507	104.322	0.000
Nail Size	1	1.233	1.233	6.273	0.013
Penetration	2	15.399	7.700	39.169	0.000
Wood Species	3	33.678	11.226	57.108	0.000
Wood Grade \times Nail Size	1	0.998	0.998	5.078	0.025
Wood Grade \times Penetration	2	4.315	2.157	10.975	0.000
Wood Grade \times Wood Species	3	0.223	0.074	0.378	0.769
Nail Size \times Penetration	1	0.748	0.748	3.806	0.052
Nail Size \times Wood Species	6	1.411	0.235	1.196	0.307
Penetration \times Wood Species	2	1.669	0.834	4.244	0.015
Grade \times Nail Size \times Penetration	3	3.366	1.122	5.708	0.001
Grade \times Nail Size \times Wood Species	6	0.721	0.120	0.611	0.721
Nail Size \times Penetration \times Wood Species	2	0.304	0.152	0.774	0.462
Grade \times Nail Size \times Penetration \times Wood	6	1.083	0.181	0.919	0.481
Error	9	3.228	0.359	1.825	0.062
Total	432	84.919	0.197		

The lack of significant two-way interactions between wood grades and wood species, nail size and penetration and nail size and wood species is an indication that wood species have relatively little effect on the withdrawal strength and that inherent characteristics such as specific gravity have greater effect. Three-way interactions for withdrawal strength were not significant, except for wood grade \times nail size \times penetration. This indicates that the withdrawal load is governed by combination of nail size, penetration and wood grade. Nail size though significant was less than that for grade, penetration and species indicating that at some point an increase in size may reduce strength, possibly through flaws such as splits.

Table 2 shows the mean comparison results for all the factors. As mentioned earlier, wood species show significant effect on the nail withdrawal strength. Cypress wood had the highest withdrawal resistance of 1.425 kN and was significantly different from that of pine wood of 1.332 kN.

For wood grades, SS grade gave nail withdrawal strength of 1.434 kN, which was significantly higher than 1.326 kN for GS grade. This difference could be attributed to the fact that for GS grade, although the wood used was visually knot free, it may have contained other invisible defects like spiral grain whose effect, although not assessed could have decreased the withdrawal strength.

Table 2: Mean comparisons for the main effects of wood species, grade, nail size and penetration

Experimental Factor	Mean Withdrawal Strength (kN)			
	Cypress	Pine		
Wood Species	1.425	1.332		
Wood Grades	SS	GS		
	1.434	1.326		
Nail length (inches)	6	4	3	
	1.599	1.391	1.145	
Penetration (mm)	30	40	50	60
	0.990	1.343*	1.476*	1.715

Values marked with an asterisk are not significantly different at 0.05 level of significance.

Figure 1 shows the trends in withdrawal load with changing nail length and wood grade. Withdrawal strengths for joints with different nail length and diameter were significantly different. Six inch (5.73mm diameter) nails produced withdrawal strengths of 1.599 kN, which was significantly higher than 1.391 kN for the four inch (3.91mm diameter) nails. The three inch long (3.10mm diameter) nails had withdrawal strength of 1.391 kN, which was significantly lower than the other two. This shows that large diameter nails would be better for joinery in terms of withdrawal resistance if the wood size is large enough to allow for their use.

Nail penetration showed a variation in terms of its effect to withdrawal strength. Withdrawal strength increased significantly with increased penetration as shown in Table 2. Sixty millimeter penetration gave the highest withdrawal strength of 1.715kN which was significantly higher than the rest. However, 40mm and 50mm penetration produced resistance of 1.343 kN and 1.476 kN respectively which were not significantly different. This indicates that the more nails penetrate into the wood, the more the resistance to withdrawal is increased. There is need however to consider the size of the wood members being joined when choosing nail length and penetration to avoid using too long or too thick nail which could crack the wood hence weakening the joint. Penetration depths not far from one another may not however have significant effect on the withdrawal resistance.

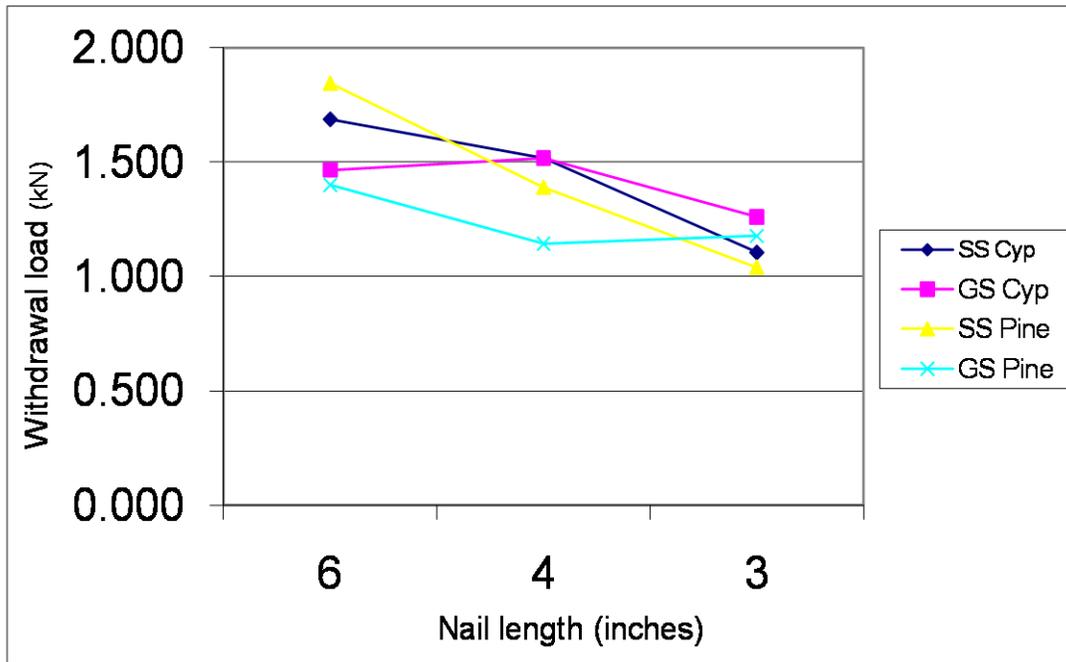


Figure 1: Influence of nail length and wood grade on withdrawal strength

The values plotted in Figure 2 are means for the four penetrations for each of the combinations of species, nail length and grade. Increased nail penetration produced increase in resistance to nail withdrawal irrespective of wood species and grade. These trends are consistent with those for related dowel-shape fasteners (Soltis et al, 1994; Yamada et al, 1991). The increase in withdrawal strength with penetration is due to the increased contact between the wood and the fastene

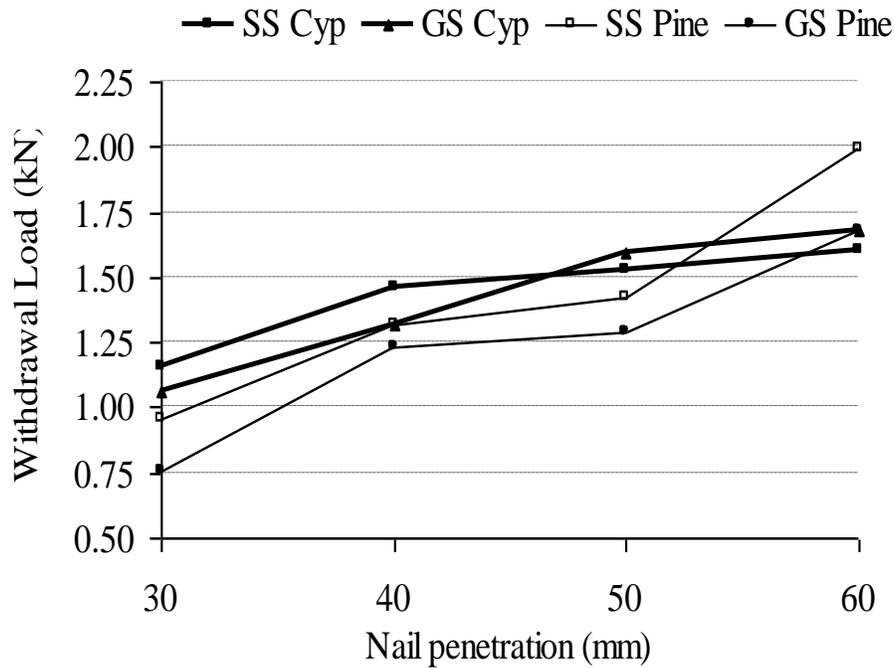


Figure 2. Influence of penetration and wood grade on withdrawal strength

Conclusions and Recommendations

Conclusions

- Resistance to nail withdrawal for nailed cypress and pine joints increases with nail diameter and penetration and the effect is dependent on the timber species and grade.
- The effect of timber grade on withdrawal strength implies that grading is important in improving performance of joinery where nails are involved since wood defects negatively affect nail withdrawal strength. There is however need to evaluate the effect of wood defects on withdrawal strength.
- The effect of wood characteristics such as grade on nail withdrawal strength is smaller than that of nail diameter and penetration

Recommendations

The data obtained from this study can be used in deriving basic loads for use in cypress and pine nailed joint design codes. There is also need to derive empirical equations for predicting the withdrawal strength for all possible nail diameters and penetrations.

Acknowledgements

Funding was provided by Plantation Forestry Research Programme of Kenya Forestry Research Institute (KEFRI) under the GoK research funds. We are indebted to Dominic Mikile, the KEFRI timber engineering senior technologist for the efforts in laboratory tests and data collection. We are also grateful to the entire KEFRI scientific editorial committee for their critique of the draft manuscript.

References

- American Soc. of Civil Engineers (ASCE). 2007. Seismic rehabilitation of existing buildings. ASCE/SEI 41-06. ASCE, Reston, VA.
- Blass H. J., 1994. Characteristics of nailed joints. *Forest Products Journal* 44(4): 33-39.
- British Standards Institute, 1989. BS 6948: British Standard Methods of Tests for Mechanically Fastened Joints in Timber and Wood Based Materials.
- Chikamai, BN., 1987a. Variation in the Wood Quality of *Pinus patula* Grown in Kenya. *East African Agriculture and Forestry Journal* 52(3): 176-183.
- Chikamai BN., Githiomi JK. and Onchieku JM., 2001. Strength Properties and Groups of Major Commercial Timbers Grown in Kenya. *Discovery and Innovation* 2001, 13 (3/4).
- Eckelman, C.A., Y.Z. Erdil, and J. Zhang. 2002. Withdrawal and Bending Strength of Dowel Joints Constructed of Plywood and Oriented Strand Board. *Forest Products Journal* 52(9):66-74.
- Kenya Bureau of Standards, 1989. KS02-771: Kenya Standard Specification for Softwood Timber Grades for Structural Use. Kenya Bureau of Standards.
- Mohamad M. A. H. and I. Smith, 1994. Stiffness of nailed OSB-to-Lumber connections. *Forest Products Journal* 44(11/12): 37-44.
- Mohamad M. A. H. and Smith, 1996. Effects of multi-phase moisture conditioning on stiffness of nailed OSB-to-Lumber connections. *Forest Products Journal* 46(4): 76-83.
- Ringo W. N., 1983. Basic Density and Tracheid Length in Juvenile and Mature Eood in *Pinus patula* from Southern Tanzania. University of Dar-es-Salaam. Division of Forestry.
- Soltis L. W., W. Nelson and S. G. Winstorfer, 1993. Static Strength of Simulated ceiling and floor connections in modular or manufactured housing. *Forest Products Journal* 43(6) 15-20.
- USDA Forest Service, 1987. Wood Handbook: Wood as an Engineering Material. Agricultural Handbook 72, Washington, DC. US. Department of Agriculture.
- Yadama V, B. M. Syed, P. H. Steele and D. E. Lyon, 1991. Effects of leg penetration on the strength of steple joint in selected wood and wood-based materials. *Forest Products Journal* 41(6) 15-20. Forest Products Research Society.
- Zhang, J., G. Li, and T. Sellers. 2003. Withdrawal and Bending Performance of Dowel Joints in Furniture-Grade Plywood. *Forest Products Journal* 53(7/8):41-49.